

QUALITY PERFORMS.

Total immersion study

Corrosion studies on **GeoBrom® HG520**

X **GeoBrom® HG520**

QUALITY **WORKS.**

LANXESS
Energizing Chemistry

BROMINATED DERIVATIVE PRODUCTS FOR MERCURY CONTROL

LANXESS
INNOVATIVE.
RELIABLE.
SUSTAINABLE.

Contents

■ BACKGROUND INFORMATION	2
■ OBJECTIVES	2
■ EXECUTIVE SUMMARY	3
■ DESCRIPTION OF TEST PROCEDURE	3
■ RESULTS AND DISCUSSION	3
■ CONCLUSION	4
■ TABLES AND FIGURES	5

Background information

A 90-day, total-immersion corrosion rate study was conducted using **GeoBrom® HG520** calcium bromide solution and six selected metals at 20° and 50°C. ASTM Method “Standard Practice for Preparing, Cleaning, and Evaluating Corrosion Test Specimens” G1–03 (reapproved 2011) was used to prepare, clean, and evaluate tests specimens.

The following six metals were evaluated:

C-1018	mild carbon steel coupon
■ 304-W	304SS welded coupon
■ 316-LW	316SS, low carbon, welded coupon
■ 2205	Duplex 2205 coupon
■ 304-LW	304SS, low carbon, welded coupon
■ 316	316SS coupon

Objectives of the study

- Establish subsurface corrosion rates at 20°C and 50°C for each metal.
- Visually document coupon condition before and after 90 day exposure.
- Analyze solution for metal content before and after 90 day exposure to evaluate metals in test solution. coupon

All specimens were less than 2.0 mpy corrosion rate based on this 90 day total-immersion study. Mild carbon steel (C-1018) had the highest rates at 0.32 mpy at 20 °C and 1.29 mpy at 50 °C. All remaining specimens were under 0.05 mpy. ICP analysis indicated elevated iron content in test solutions at the end of the 90 day period. General surface corrosion was observed on both C1018 coupons with some pitting at 50 °C. There was no visible corrosion on remaining test specimens. The maximum allowable corrosion rate for each specimen with **GeoBrom® HG520** depends on the application.

Description of test procedure

Metal test coupons with dimensions of ~ 2.0" x 0.75" x 0.125" were supplied by an outside vendor. The vendor prepared the coupons by abrading surfaces and stamping metal type and marking specimens with a unique identification number. Prior to using, coupons were cleaned using reagent grade aqueous HCl and a bristle brush followed by a thorough deionized water rinse, degreased using acetone, dried using hot air, then allowed to cool in desiccators. The clean, dry specimens were weighed and measured. Using forceps, a four place OHAUS Galaxy Model G160D analytical balance was used to attain initial weights for all coupons. Dimensions were established using a Starrett® Micrometer part # 436RL-1, EDP 51568 and a Starrett® Dial Caliper Part # 120Z, EDP 55951. Three measurements were taken on all dimensions and averaged for the length, width, and thickness. Pictures were taken to record coupon condition prior to beginning immersion tests. Test coupons were split into two groups containing specimens of each metal type, and placed into two glass one-liter bottles with Teflon® liners. One group was placed in a Yamato Model DVS600 drying oven to hold samples at 50 °C, and the second group was placed in a controlled environment room held at 20 °C. There was no agitation or aeration of the test specimens while in the glass bottles.

Duration of the test was 90 days or 2,160 hours. Prior to cleaning, pictures were taken to record coupon condition after the 90 day immersion test. After cleaning, pictures were taken again. None of the specimens were heavily corroded, so post immersion cleaning was simple and consisted of the following:

- Immersion in deionized water to remove test solution
- Immersion and brushed in aq. HCl (for mild carbon steel), and nitric acid (for the stainless steels)
- Thoroughly rinsed with deionized water, then immediately dried.

The C1018 coupon required scrubbing with a mild abrasive in deionized water. Table A1.1 in ASTM G1-03 was used as a guide to select cleaning procedure for removal of corrosion products. After drying test specimens with hot air and then allowing them to cool in desiccators, all specimens were re-weighed and the final weights recorded.

Spreadsheets were developed to capture data and to make calculations per ASTM method. Calculated metal densities and published metal densities were used in corrosion rate calculations for comparison.

The average corrosion rate calculation per ASTM G1-03 is:

$$\text{Corrosion rate} = (K \times W) / (A \times T \times D)$$

- K = a constant "(K) constant listed in ASTM G1-03, Section 8 for desired units"
- T = time of exposure in hours
- A = area in cm²
- W = mass loss in grams
- D = density in gm/cm³

Results and discussion

Tables 1 and 2 provide data on test specimens at 20°C and at 50°C, respectively. Corrosion rates on all specimens were under 2.0 mpy rate. Mild carbon steel C-1018 gave the highest corrosion rate at 0.32 mpy at 20°C and 1.29 mpy at 50°C. General surface corrosion was observed on C-1018 coupons with some pitting on the C-1018 coupon at 50°C. There was no surface corrosion or pitting observed visually on any remaining specimens.

Corrosion rates for each specimen were charted to reflect trends over the two temperatures 20°C and 50°C (see Figures 1-2).

GeoBrom® HG520 test solutions were also submitted for inductively coupled plasma (ICP) analysis before and after the immersion test. ICP data contained in Table 3 provides metals concentrations in test fluids at start, at end, and the difference between the two. There is a significant increase in iron (Fe) concentrations in the post- test solutions from the corrosion of the carbon steel coupons.

To visually document condition of test specimens, pictures were taken before immersion tests, after, then after cleaning (see Figures 3-10).

Table 4 shows the chemical composition of each test specimen.

Conclusion

C-1018 showed signs of corrosion in this test. There are a number of different corrosion standards depending on the application. Therefore, whether C-1018 is suitable for use with CaBr₂ depends on the application. These data are relevant only to the 52% CaBr₂ solution. Dilute solutions or other uses of 52% solution may exhibit different corrosive behaviors.

Table 1: Subsurface at 20 °C
Corrosion coupon testing with GeoBrom® HG520 solution – below surface at 20 °C

May 31, 2013 – August 29, 2013

Total exposure time: 90 days

Using ASTM designation: G1–03 (reapproved 2011) standard practice for preparing, cleaning, and evaluating corrosion test specimens

Coupon type	C-1018	304-W	316-LW	Duplex 2205	304-LW	316
Identification mark	A1686	A0023	A8151	single dot	A0012	A1170
Weight (grams)	22.1947	22.8463	20.0253	21.9995	22.9181	19.7559
Length (inches)	2.017	2.003	2.003	2.017	2.008	1.989
Width (inches)	0.771	0.756	0.746	0.763	0.759	0.750
Thickness (inches)	0.123	0.129	0.115	0.123	0.130	0.112
Hole dia. (inches)	0.376	0.375	0.377	0.377	0.375	0.380
Calculated density (gm/cc)	7.627	7.674	7.719	7.674	7.641	7.792
Published density (gm/cc) ASTM	7.86	7.94	7.94	7.805	7.94	7.98
Calculated surface area (sq. cm)	23.991	23.714	22.776	23.757	23.844	22.607
Start date (MDY)	5/31/2013	5/31/2013	5/31/2013	5/31/2013	5/31/2013	5/31/2013
Start time (hours)	14:35	14:35	14:35	14:35	14:35	14:35
End date (MDY)	8/29/2013	8/29/2013	5/31/2013	5/31/2013	5/31/2013	8/29/2013
End time (hours)	14:35	14:35	14:35	14:35	14:35	14:35
Temperature (°C)	20	20	20	20	20	20
Exposure time (hours)	2,160	2,160	2,160	2,160	2,160	2,160
Ending weight (grams)	22.1585	22.8455	20.0233	21.9992	22.9161	19.7551
Loss in weight (grams)	0.0362	0.0008	0.002	0.0003	0.002	0.0008
Rate of corrosion (mpy) using calculated density	0.3160	0.0070	0.0182	0.0026	0.0175	0.0073
Rate of corrosion (mpy) using published density	0.3066	0.0068	0.0177	0.0026	0.0169	0.0071

Observations :

- Mild carbon steel shows the highest corrosion rate at 0.316 mpy at 20°C based on a 90-day exposure time.
- Coupons of 304-W, 316-LW, Duplex 2205, 304-LW, and 316 were all below 0.05 mpy.

Table 2: Subsurface at 50 °C
Corrosion coupon testing with GeoBrom® HG520 solution – below surface at 50 °C

May 31, 2013 - August 29, 2013

Total exposure time: 90 days

Using ASTM designation: G1–03 (reapproved 2011) standard practice for preparing, cleaning, and evaluating corrosion test specimens

Coupon type	C-1018	304-W	316-LW	Duplex 2205	304-LW	316
Identification mark	A1685	A0024	A8153	double dot	A0013	A1169
Weight (grams)	22.3493	23.0076	20.17	21.9338	22.7433	19.9863
Length (inches)	2.018	2.005	2.000	2.017	2.006	2.001
Width (inches)	0.773	0.760	0.749	0.762	0.758	0.750
Thickness (inches)	0.124	0.130	0.115	0.122	0.129	0.113
Hole dia. (inches)	0.375	0.373	0.377	0.378	0.375	0.380
Calculated density (gm/cc)	7.574	7.637	7.694	7.697	7.657	7.757
Published density (gm/cc) ASTM	7.86	7.94	7.94	7.805	7.94	7.98
Calculated surface area (sq. cm)	24.127	23.867	22.870	23.702	23.760	22.797
Start date (MDY)	5/31/2013	5/31/2013	5/31/2013	5/31/2013	5/31/2013	5/31/2013
Start time (hours)	14:35	14:35	14:35	14:35	14:35	14:35
End date (MDY)	8/29/2013	8/29/2013	8/29/2013	8/29/2013	8/29/2013	8/29/2013
End time (hours)	14:35	14:35	14:35	14:35	14:35	14:35
Temperature (°C)	50	50	50	50	50	50
Exposure time (hours)	2,160	2,160	2,160	2,160	2,160	2,160
Ending weight (grams)	22.2015	23.0066	20.1696	21.9322	22.7382	19.9855
Loss in weight (grams)	0.1478	0.001	0.0004	0.0016	0.0051	0.0008
Rate of corrosion (mpy) using calculated density	1.2918	0.0088	0.0036	0.0140	0.0448	0.0072
Rate of corrosion (mpy) using published density	1.2448	0.0084	0.0035	0.0138	0.0432	0.0070

Observations :

- Mild carbon steel shows the highest corrosion rate at 1.2918 mpy at 50 °C based on a 90-day exposure time.
- Coupons of 304-W, 316-LW, Duplex 2205, 304-LW, and 316 were all below 0.05 mpy.

Table 3: Metals in test fluid
ICP analysis before and after 90-day total-immersion corrosion rate study


All results in mg/L

Metal ID	ref ICP spl #1	ref ICP spl #3	ref ICP spl #2		ref ICP spl #4	Difference
	Metals in sample	Metals in sample	20°C test	Metals in sample	Metals in sample	
	B-04 before	B-04 after at 20°C	Difference	B-05 before	B-05 after at 50°C	
Ag (Silver)	4.23	4.85	0.62	4.26	4.81	0.55
Al (Aluminum)	3.78	4.75	0.97	3.89	4.42	0.53
As (Arsenic)	8.77	0.00	-8.77	3.55	5.12	1.57
B (Boron)	0.92	1.05	0.13	1.04	1.11	0.07
Ba (Barium)	5.72	5.88	0.16	5.78	5.93	0.15
Be (Beryllium)	0.00	0.00	0.00	0.00	0.00	0.00
Bi (Bismuth)	10.97	9.97	-1.00	11.97	11.83	-0.14
Ca (Calcium)	very high	very high	N/A	very high	very high	N/A
Cd (Cadmium)	1.14	2.24	1.10	1.70	2.93	1.23
Ce (Cerium)	13.64	15.37	1.73	16.25	15.56	-0.69
Co (Cobalt)	3.25	3.12	-0.13	3.41	3.17	-0.24
Cr(II) (Chromium)	6.69	5.17	-1.52	5.78	8.86	3.08
Cu (Copper)	1.50	1.45	-0.05	1.40	1.54	0.14
Fe(II) (Iron)	3.25	53.95	50.70	6.39	139.86	133.47
K (Potassium)	168.11	166.39	-1.72	149.46	184.31	34.85
La (Lanthanum)	61.13	61.93	0.80	66.21	62.88	-3.33
Li (Lithium)	6.15	6.41	0.26	6.48	6.29	-0.19
Mn (Manganese)	3.51	4.47	0.96	3.58	7.00	3.42
Mo (Molybdenum)	11.03	11.99	0.96	9.44	10.15	0.71
Na (Sodium)	3.36	3.49	0.13	3.34	3.75	0.41
Ni (Nickel)	3.55	2.40	-1.15	3.29	2.71	-0.58
Pb (Lead)	4.22	4.83	0.61	6.30	12.99	6.69
Rb (Rubidium)	4.74	4.32	-0.42	4.74	5.09	0.35
Sb (Antimony)	5.27	4.63	-0.64	3.28	7.96	4.68
Se (Selenium)	uncal	uncal	N/A	uncal	uncal	N/A
Sn (Tin)	6.57	6.48	-0.09	6.66	10.79	4.13
Sr (Strontium)	52.08	61.19	9.11	52.39	68.60	16.21
Ti (Titanium)	2.93	3.03	0.10	2.90	3.03	0.13
Tl (Thallium)	uncal	uncal	N/A	uncal	uncal	N/A
U (Uranium)	48.57	29.68	-18.89	43.04	38.00	-5.04
V (Vanadium)	18.32	21.79	3.47	21.39	29.99	8.60
Zn(I) (Zinc)	0.00	0.46	0.46	0.00	3.98	3.98

Note: Metals highlighted in the table are major components in the coupons evaluated. Significant increases in the concentration of these metals would be an indication of corrosion of the coupons

**Figure 1: Corrosion rate trend chart
(with Y axis at 0 to 1.4 mpy scale)**

**Corrosion coupons at 20°C and 50°C subsurface in
GeoBrom® HG520 calcium bromide solution**

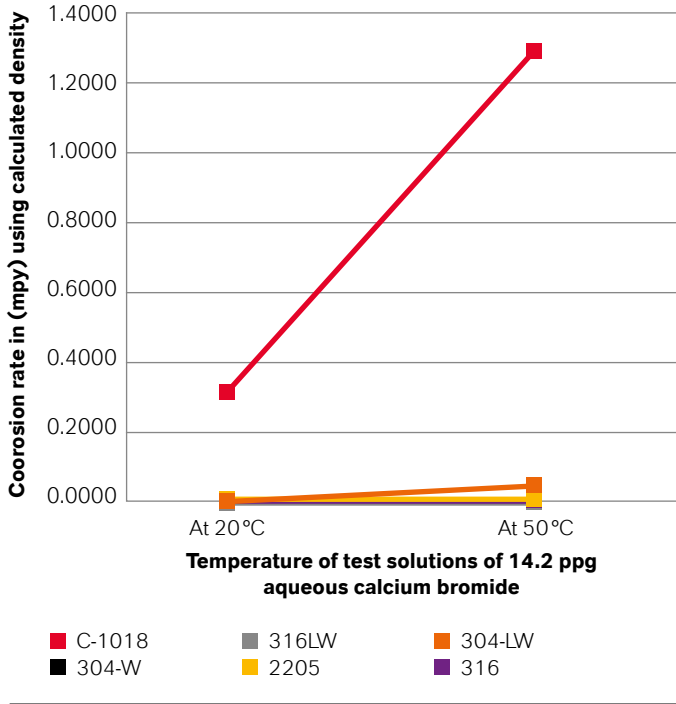

**Figure 2: Corrosion rate trend chart
(with Y axis at 0 to 0.07 mpy scale)**

**Corrosion coupons at 20°C and 50°C subsurface in
GeoBrom® HG520 calcium bromide solution**

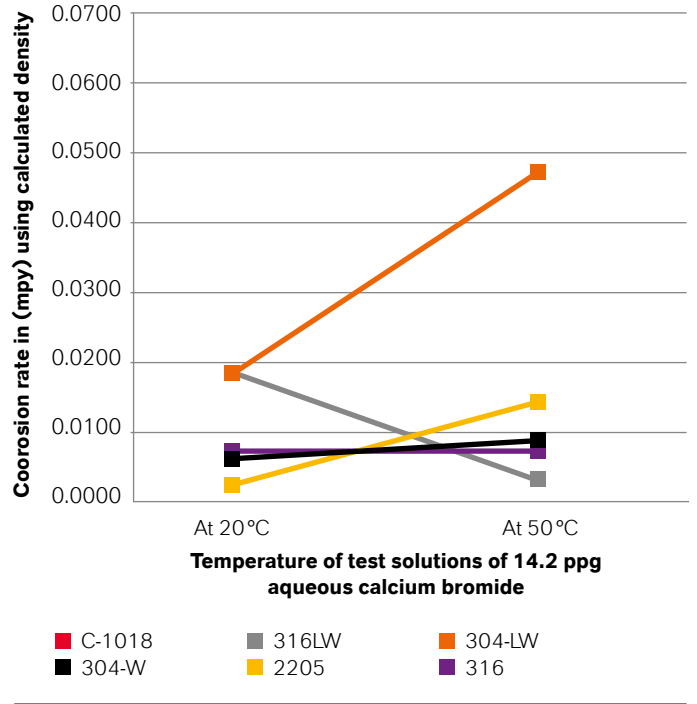


Figure 3: Test coupons before 90-day subsurface exposure

Length	Width	Thickness	Hole dime	Grams to weight		
2.015"	0.771"	0.123"				C1018
2.020"	0.771"	0.124"	0.376"	22.1947gm		
2.015"	0.771"	0.122"				C1018
2.017"	0.7735"	0.125"				
2.020"	0.774"	0.124"	0.375"	22.3493 gm		
2.017"	0.773"	0.1235"				Duplex 2205
2.017"	0.763"	0.1225"				
2.018"	0.765"	0.1225"	0.377"	21.9995 gm		
2.016"	0.762"	0.1225"				
2.017"	0.762"	0.122"				Duplex 2205
2.017"	0.764"	0.122"	0.378"	21.9338 gm		
2.017"	0.761"	0.122"				
2.004"	0.753"	0.129"				304W
2.004"	0.757"	0.130"	0.375"	22.8463 gm		
2.002"	0.759"	0.129"				
2.005"	0.758"	0.130"				304W
2.007"	0.760"	0.129"	0.373"	23.0076 gm		
2.004"	0.761"	0.131"				

Figure 4: Test coupons before 90-day subsurface exposure

Length	Width	Thickness	Hole dime	Grams to eeight		
2.006"	0.757"	0.1305"				
2.010"	0.760"	0.129"	0.375"	22.9181gm		304LW
2.007"	0.760"	0.1295"				
2.003"	0.757"	0.127"				
2.007"	0.758"	0.127"	0.375"	22.7433 gm		304LW
2.007"	0.760"	0.1275"				
1.990"	0.749"	0.112"				
1.989"	0.754"	0.112"	0.380"	19.7559 gm		316
1.987"	0.752"	0.113"				
2.001"	0.750"	0.113"				
2.000"	0.752"	0.114"	0.380"	19.9863 gm		316
2.002"	0.748"	0.113"				
2.000"	0.746"	0.115"				
2.004"	0.747"	0.1135"	0.377"	20.0253 gm		316LW
2.005"	0.745"	0.115"				
1.997"	0.750"	0.115"				
2.003"	0.750"	0.115"	0.377"	20.1700 gm		316LW
2.000"	0.748"	0.116"				

Figure 5: Test coupons after 90-day subsurface exposure at 20°C (before cleaning)

Subsurface at 20°C out 8-29-13 at 14:45 – not cleaned

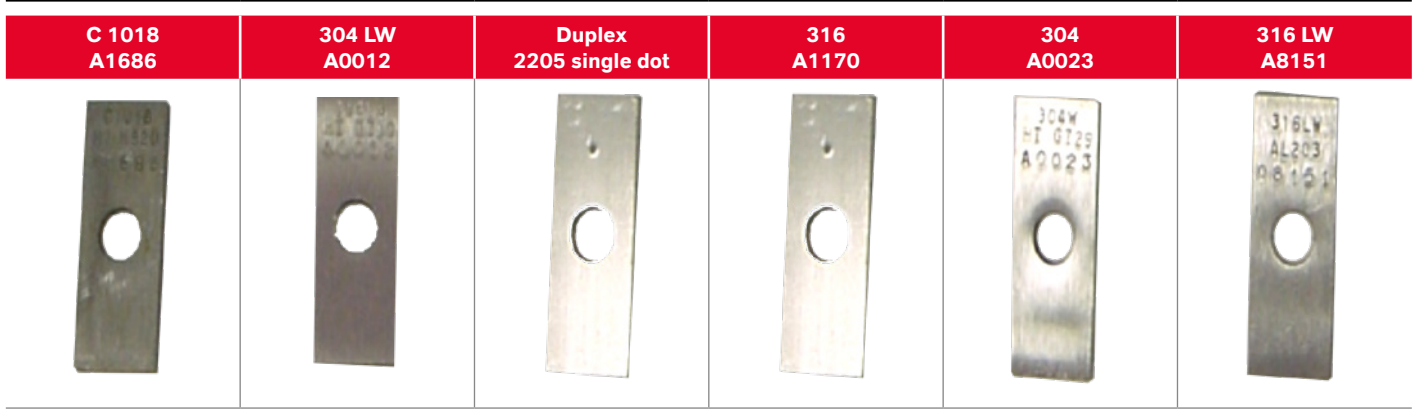


Figure 6: Test coupons after 90-day subsurface exposure at 50°C (before cleaning)

Subsurface at 20°C out 8-29-13 at 14:45 – not cleaned

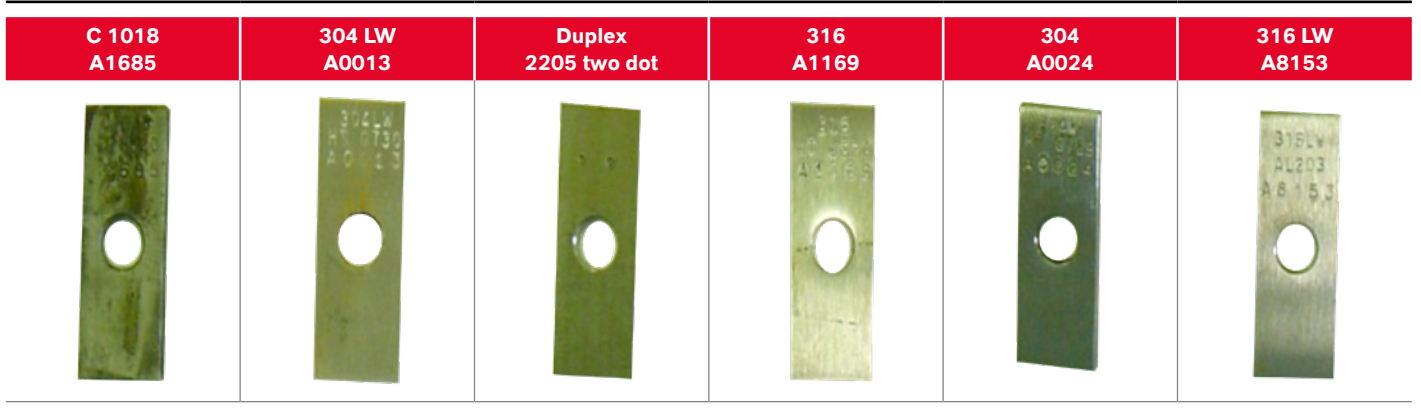


Figure 7: Front side of C1018 coupon after 90-day subsurface exposure at 50°C (before cleaning)



Figure 8: Back side of C1018 coupon after 90-day subsurface exposure at 50°C (before cleaning)



Figure 9: Test coupons after 90-day subsurface exposure at 20°C (after cleaning)

Subsurface at 20°C out 8-29-13 at 14:45

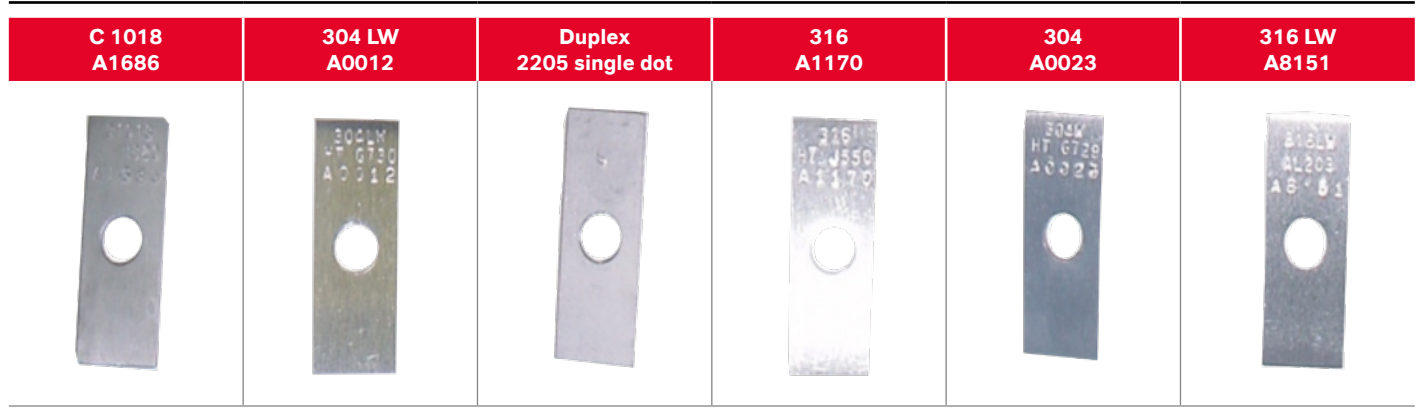


Figure 10: Test coupons after 90-day subsurface exposure at 50°C (after cleaning)

Subsurface at 50°C out 8-29-13 at 14:45

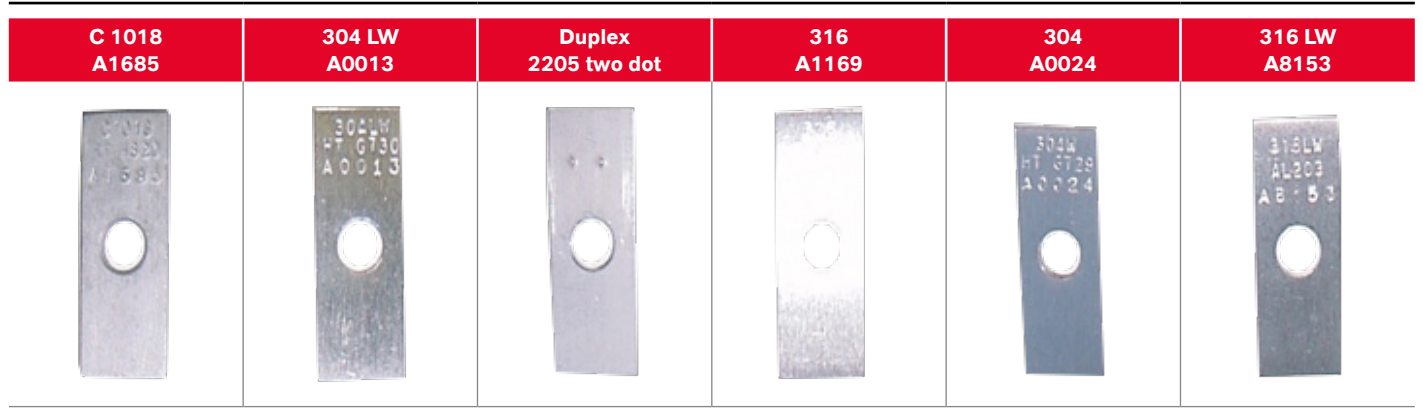


Table 4: Composition of specimens

Chemical composition of specimens tested during 90-day total immersion study

AISI = American Iron and Steel Institute

Data in % by weigh

Metal type	AISI 1018	AISI 304	AISI 304-L	AISI 316	AISI 316-L	Duplex 2205
Carbon	0.15 - 0.20	0.08 max	0.03 max	0.08 max	0.03 max	<0.03
Manganese	0.60 - 0.90	2 max	2 max	2 max	3 max	< 2
Phosphorus	0.040 max	0.045 max	0.045 max	0.045 max	0.045 max	< 0.03
Sulfur	0.050 max	0.03 max	0.03 max	0.03 max	0.03 max	< 0.02
Silicon	0.15 to 0.30	0.75 max	0.75 max	1 max	2 max	< 1
Chromium	N/A	18 - 20	18-20	16 - 18	17 - 18	21 - 23
Nickel	N/A	8 to 12	8 to 12	10 to 14	11 to 14	4.5 - 6.5
Molybdenum	N/A	N/A	N/A	2 to 3	2 to 3	2.5 - 3.5
Nitrogen	N/A	0.10 max	0.10 max	N/A	N/A	0.8 - 2.0
Iron	balance	balance	balance	balance	balance	balance



LANXESS Corporation

Business Unit Additives
111 RIDC Park West Drive
Pittsburgh, PA 15275-1112
USA
Phone: +1 412-809-1000

polymer.additives@lanxess.com
<http://add.lanxess.com>

The manner in which you use and the purpose to which you put and utilize our products, technical assistance and information (whether verbal, written or by way of production evaluations), including any suggested formulations and recommendations are beyond our control. Therefore, it is imperative that you test our products, technical assistance and information to determine to your own satisfaction whether they are suitable for your intended uses and applications. This application-specific analysis must at least include testing to determine suitability from a technical as well as health, safety, and environmental standpoint. Such testing has not necessarily been done by us. Unless we otherwise agree in writing, all products are sold strictly pursuant to the terms of our standard conditions of sale. All information and technical assistance is given without warranty or guarantee and is subject to change without notice. It is expressly understood and agreed that you assume and hereby expressly release us from all liability, in tort, contract or otherwise, incurred in connection with the use of our products, technical assistance, and information. Any statement or recommendation not contained herein is unauthorized and shall not bind us. Nothing herein shall be construed as a recommendation to use any product in conflict with patents covering any material or its use. No license is implied or in fact granted under the claims of any patent.

Health and Safety Information: Appropriate literature has been assembled which provides information concerning the health and safety precautions that must be observed when handling the LANXESS products mentioned in this publication. For materials mentioned which are not LANXESS products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be followed. Before working with any of these products, you must read and become familiar with the available information on their hazards, proper use, and handling. This cannot be overemphasized. Information is available in several forms, e.g., material safety data sheets and product labels. Consult your LANXESS Solutions US Inc. representative or contact the Product Safety and Regulatory Affairs Department at LANXESS.

Regulatory Compliance Information: Some of the end uses of the products described in this publication must comply with applicable regulations, such as the FDA, NSF, USDA, CPSC and BfR. If you have any questions on the regulatory status of these products, contact your LANXESS Solutions US Inc. representative or Regulatory Affairs Manager at LANXESS.

Note: The information contained in this publication is current as of June, 2018. Please contact LANXESS Solutions US Inc. to determine if this publication has been revised.

© = trademark of LANXESS Deutschland GmbH or its affiliates, registered in many countries in the world.